

## Structural and Dielectric Behaviour of Mn-Zn Er ferrites

\*Rajesh Jain

### Abstract

Dielectric properties such as dielectric constant ( $\epsilon'$ ) and dielectric loss tangent ( $\tan \delta$ ) of mixed Mn-Zn-Er ferrites having the compositional formula  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Fe}_{2.05-x}\text{Er}_x\text{O}_4$  (where  $x = 0.2, 0.4, 0.6, 0.8$  and  $1.0$ ) were measured at room temperature in the frequency range 1–13 MHz using a HP 4192A impedance analyser. Plots of dielectric constant ( $\epsilon'$ ) vs frequency show a normal dielectric behaviour of spinel ferrites. The frequency dependence of dielectric loss tangent ( $\tan \delta$ ) was found to be abnormal, giving a peak at certain frequency for all mixed Mn-Zn-Er ferrites. A qualitative explanation is given for the composition and frequency dependence of the dielectric constant and dielectric loss tangent. Plots of dielectric constant vs temperature have shown a transition near the Curie temperature for all the samples of Mn-Zn-Er ferrites. However,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$  does not show a transition. On the basis of these results an explanation for the mechanism in Mn-Zn-Er ferrites is suggested.

**Keywords:** Dielectric constant; dielectric loss tangent; Mn-Zn-Er ferrites; electrical resistivity.

### 1. Introduction

The dependence of dielectric properties of Li-Mg-Zn ferrites as a function of frequency, composition and temperature has been studied (Shaikh *et al* 1999). The dielectric behaviour of the Ni-Zn (where  $0 \leq x \leq 1$ ) as a function of frequency, composition and temperature was reported (Abdun 1999). The dielectric behaviour of the Ba-Ni-Zn ferrites also as a function of temperature and frequency was reported (Elata *et al* 1999). The dielectric properties of Ni-Zn ferrites as a function of sintering temperature, sintering time and frequency have been investigated (Rao and Rao 1997). A strong correlation between conduction mechanism and the dielectric behaviour of ferrites has been reported (Iwauchi 1971). The dielectric properties of Mg-Zn ferrites were investigated (Ravinder and Lata 1999). With a view to the understanding of dielectric phenomena in mixed Mn-Zn-Er ferrites, a systematic study of dielectric properties as a function of frequency, composition and temperature was undertaken and the results of the study are presented in this paper.

### 2. Experimental

Polycrystalline mixed Mn-Zn-Er ferrites having the chemical formula  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Fe}_{2.05-x}\text{Er}_x\text{O}_4$  (where  $x = 0.2, 0.4, 0.6, 0.8$  and  $1.0$ ) were prepared by a conventional double sintering ceramic method. X-ray diffractometer studies of the samples using  $\text{CuK}\alpha$  radiation of Rigaku DMAX II X-ray Diffractometer confirmed the spinel formation. The dielectric measurements were made in the frequency range 1–13 MHz using impedance analyser (Model HP4192 A of Hewlett-Packard). The value of the dielectric constant ( $\epsilon'$ ) of the ferrite sample is calculated using the formula

$$\epsilon' = \frac{C \times f}{\epsilon_0 \cdot A}, \quad (1)$$

---

### Structural and Dielectric Behaviour of Mn-Zn Er ferrites

Rajesh Jain

where  $\epsilon_0$  is an electrical constant equal to  $8.854 \times 10^{-2}$  pF/cm,  $C$  the capacitance of the specimen in cm,  $t$  the thickness of the specimen in cm and  $A$  the area of the specimen in sq-cm. The complex dielectric constant ( $\epsilon''$ ) of the ferrite sample is given by

$$\epsilon'' = \epsilon' \tan \delta. \quad (2)$$

The Curie temperature,  $T_c(K)$  of the samples was determined by the gravity method.

### 3. Results and discussion

#### 3.1 Composition dependence of dielectric behaviour

The room temperature values of the dielectric constant ( $\epsilon'$ ), dielectric loss tangent ( $\tan \delta$ ) and complex dielectric constant ( $\epsilon''$ ) of mixed Mn–Zn–Er ferrites as derived from the experiments are given in table 1. The values of electrical conductivity ( $\sigma$ ) and  $\text{Fe}^{2+}$  concentration are also included in the table to facilitate discussion. It can be seen from the table that the  $\epsilon'$ ,  $\tan \delta$  and  $\epsilon''$  of the mixed

**Table 1.** Composition dependence of room temperature dielectric data for erbium substituted Mn–Zn–Er ferrites at 1 MHz.

Sample no.	Ferrite composition	$\epsilon'$	$\tan \delta$	$\epsilon''$	$\sigma$ ( $\Omega^{-1}\cdot\text{cm}^{-1}$ )	$\text{Fe}^{2+}$ composition (%)
1.	$\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.2}\text{Fe}_{1.85}\text{O}_4$	276	0.32	88.32	$1.58 \times 10^{-7}$	1.24
2.	$\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.4}\text{Fe}_{1.65}\text{O}_4$	124	0.16	19.84	$5.86 \times 10^{-9}$	0.92
3.	$\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.6}\text{Fe}_{1.45}\text{O}_4$	224	0.24	53.76	$5.05 \times 10^{-8}$	1.18
4.	$\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.8}\text{Fe}_{1.25}\text{O}_4$	338	0.42	141.96	$8.56 \times 10^{-7}$	1.32
5.	$\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$	446	0.52	231.92	$2.00 \times 10^{-5}$	1.68


Mn–Zn–Er ferrites decreases with decreasing concentration of  $\text{Fe}^{2+}$  ions till the concentration ( $x$ ) of erbium is equal to 0.4. Beyond  $x = 0.4$ , these parameters show an increase with increase of erbium content. Among all the ferrites, the specimen with the composition  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$  exhibits the highest value of dielectric constant.

Further, it can be seen that  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.4}\text{Fe}_{1.65}\text{O}_4$ , which has the lowest  $\text{Fe}^{2+}$  concentration, exhibits the lowest dielectric constant, the lowest dielectric loss tangent and the lowest complex dielectric constant. The dielectric studies of Gd<sup>3+</sup> substituted copper–cadmium ferrites as a function of composition and frequency was investigated by Kolekar *et al* (1995). Ramana Reddy *et al* (1999) have investigated the dielectric behaviour of Ni–Zn ferrites as a function of temperature and frequency. Iwauchi (1971) reported a strong correlation between the conduction mechanism and the dielectric behaviour of the ferrites starting with the conjecture that the mechanism of the polarization process in ferrites is similar to that of the conduction process (Rabinkin and Novikova 1960). They observed that the electronic exchange between  $\text{Fe}^{2+} \leftrightarrow \text{Fe}^{3+}$  results in local displacements which determine the polarization behaviour of the ferrites.

### Structural and Dielectric Behaviour of Mn-Zn Er ferrites

Rajesh Jain

A similar explanation is proposed for the composition dependence of the dielectric constants of the ferrites under this investigation. It can be observed from table 1 that the composition,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$ , has the maximum divalent iron ion concentration among all the mixed Mn–Zn–Er ferrites. Correspondingly the dielectric constant for this specimen has a maximum value of 446 at 1 MHz. This high value can be explained on the basis of the fact that it has maximum number of ferrous ions which involve in the phenomenon of exchange  $\text{Fe}^{2+} \leftrightarrow \text{Fe}^{3+}$  giving rise to maximum dielectric polarization. Table 1 reveals that the variation of the dielectric constant of Mn–Zn–Er ferrites runs parallel to the variation of available ferrous ions on octahedral sites. It is significant to note that  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.4}\text{Fe}_{1.65}\text{O}_4$  which has the lowest ferrous ion concentration also possesses the lowest dielectric constant. It is also pertinent to mention that the variation of electrical conductivity with composition (table 1)

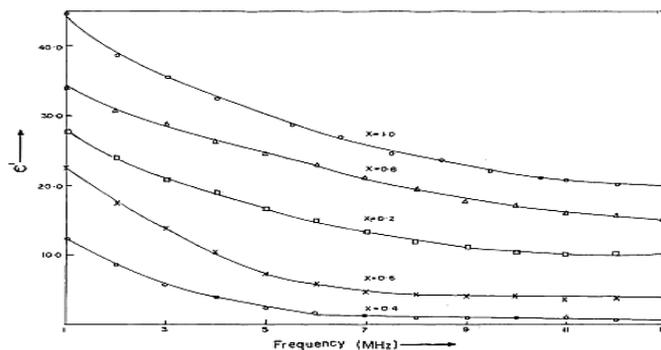

**Figure 1.** Plot of dielectric constant ( $\epsilon'$ ) against frequency for  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_x\text{Fe}_{2.05-x}\text{O}_4$  (where  $x = 0.2, 0.4, 0.6, 0.8$  and  $1.0$ ).

parallels the variation of ferrous ion concentration (Ravinder 1988). Thus, it is the number of ferrous ions on the octahedral sites that play a dominant role in the processes of conduction as well as dielectric polarization. This result is in agreement with the assumption made earlier (Rabinkin and Novikova 1960).

### 3.2 Frequency dependence of dielectric constant ( $\epsilon'$ )

The variations of dielectric constant as a function of frequency for mixed Mn–Zn–Er ferrites with different compositions is shown in figure 1. It can be seen from the figure that the value of dielectric constant decreases continuously with increasing frequency. The dispersion of dielectric constant is maximum for  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$ .

The decrease of dielectric constant with increase of frequency as observed in the case of mixed Mn–Zn–Er ferrites is a normal dielectric behaviour. This normal dielectric behaviour was also observed by several other investigators (Chandra Prakash and Bajal 1985; Ravinder 1993; Ramana Reddy *et al* 1999). The normal dielectric behaviour of spinel ferrites was also explained by Rezlescu and Rezlescu (1974). Following their work, the dependence of the dispersion of the dielectric constant on composition can be explained. The observation that  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$  shows a maximum dielectric dispersion


## Structural and Dielectric Behaviour of Mn-Zn Er ferrites

Rajesh Jain

among the mixed Mn–Zn–Er ferrites may be explained on the basis of the available ferrous ions on octahedral sites. In the case of  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$  the ferrous ion content is higher than in other mixed Mn–Zn–Er ferrites. As a consequence, it is possible for these ions to be polarized to the maximum possible extent. Further, as the frequency of the externally applied electric field decreases gradually, and though the same number of ferrous ions is present in the ferrite material, the dielectric constant ( $\epsilon'$ ) decreases from 446 at 1 MHz to 200 at 13 MHz. This reduction occurs because beyond a certain frequency of the externally applied electric field, the electronic exchange between ferrous and ferric ions i.e.  $\text{Fe}^{2+} \leftrightarrow \text{Fe}^{3+}$  can not follow the alternating field. The variation of the dispersion of  $\epsilon'$  with composition can also be explained on the same lines as above.

### 3.3 Variation of dielectric loss tangent ( $\tan \delta$ ) with frequency

Figure 2 shows the variation of  $\tan \delta$  with frequency for mixed Mn–Zn–Er ferrites. It can be seen from the figures

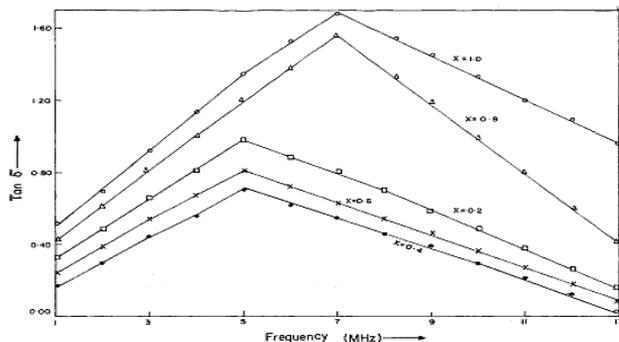

**Figure 2.** Plot of dielectric loss tangent ( $\tan \delta$ ) against frequency for  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_x\text{Fe}_{2.05-x}\text{O}_4$  (where  $x = 0.2, 0.4, 0.6, 0.8$  and  $1.0$ ).

that in the case of  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.2}\text{Fe}_{1.85}\text{O}_4$ ,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.4}\text{Fe}_{1.65}\text{O}_4$  and  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.6}\text{Fe}_{1.45}\text{O}_4$ ,  $\tan \delta$  shows a maximum at 5 MHz and for  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.8}\text{Fe}_{1.25}\text{O}_4$  and  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$ ,  $\tan \delta$  shows a maximum at 7 MHz. A qualitative explanation can be given for the occurrence of the maximum in the  $\tan \delta$  vs frequency curves in the case of mixed Mn–Zn–Er ferrites. As pointed out by Iwauchi (1971), there is a strong correlation between the conduction mechanism and the dielectric behaviour of ferrites. The conduction mechanism in  $n$ -type ferrites is considered as due to hopping of electrons between  $\text{Fe}^{2+}$  and  $\text{Fe}^{3+}$ . As such, when the hopping frequency is nearly equal to that of the frequency of externally applied electric field, a maximum of loss tangent may be observed. Thus, in the case of  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.2}\text{Fe}_{1.85}\text{O}_4$ ,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.4}\text{Fe}_{1.65}\text{O}_4$ ,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.6}\text{Fe}_{1.45}\text{O}_4$ ,  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{0.8}\text{Fe}_{1.25}\text{O}_4$  and  $\text{Mn}_{0.58}\text{Zn}_{0.37}\text{Er}_{1.0}\text{Fe}_{1.05}\text{O}_4$ , the hopping frequencies are of the appropriate magnitude, to observe a loss maximum at 5 MHz and 7 MHz, respectively.

The condition for observing a maximum in the dielectric losses of a dielectric material is given by

---

## Structural and Dielectric Behaviour of Mn-Zn Er ferrites

Rajesh Jain

$$w\tau = 1, \tag{3}$$

where  $w$  is the  $2\pi f_{\max}$  and  $\tau$  the relaxation time. Now the relaxation time  $\tau$  is related to the jumping probability per unit time  $p$ , by an equation

$$\tau = \frac{1}{2} p \quad \text{or} \quad f_{\max} \propto p. \tag{4}$$


Equation (4) shows that  $f_{\max}$  is proportional to the jumping or hopping probability. Now an increase of  $f_{\max}$  with increasing erbium content indicates that the hopping or jumping probability per unit time increases with erbium content.

**3.4 Relationship between dielectric constant ( $\epsilon'$ ) and resistivity ( $\rho$ )**

The computed values of resistivity ( $\rho$ ),  $\sqrt{\rho}$  and  $\epsilon'\sqrt{\rho}$  are given in table 2 along with the value of  $\epsilon'$  and  $\tan \delta$ . It can be seen from the table that  $\epsilon'$  is approximately inversely proportional to the square root of resistivity. As such the

**Table 2.** Variation of dielectric constant ( $\epsilon'$ ),  $\tan \delta$  and resistivity ( $\rho$ ) in the case of mixed Mn–Zn–Er ferrites.


Sample no.	Ferrite composition	$\epsilon'$	$\tan \delta$	$\rho$ ( $\Omega\cdot\text{cm}$ )	$\sqrt{\rho}$ ( $\Omega^{1/2}\cdot\text{cm}^{1/2}$ )	$\epsilon'\sqrt{\rho}$ ( $\Omega^{1/2}\cdot\text{cm}^{1/2}$ )
1.	Mn <sub>0.58</sub> Zn <sub>0.37</sub> Er <sub>0.2</sub> Fe <sub>1.85</sub> O <sub>4</sub>	276	0.32	$6.33 \times 10^6$	$2.52 \times 10^3$	$6.95 \times 10^5$
2.	Mn <sub>0.58</sub> Zn <sub>0.37</sub> Er <sub>0.4</sub> Fe <sub>1.65</sub> O <sub>4</sub>	124	0.16	$17.06 \times 10^7$	$1.31 \times 10^4$	$16.24 \times 10^3$
3.	Mn <sub>0.58</sub> Zn <sub>0.37</sub> Er <sub>0.6</sub> Fe <sub>1.45</sub> O <sub>4</sub>	224	0.24	$1.98 \times 10^7$	$0.44 \times 10^4$	$9.85 \times 10^3$
4.	Mn <sub>0.58</sub> Zn <sub>0.37</sub> Er <sub>0.8</sub> Fe <sub>1.25</sub> O <sub>4</sub>	338	0.42	$1.16 \times 10^6$	$1.08 \times 10^3$	$3.65 \times 10^3$
5.	Mn <sub>0.58</sub> Zn <sub>0.37</sub> Er <sub>1.0</sub> Fe <sub>1.05</sub> O <sub>4</sub>	446	0.52	$0.2 \times 10^5$	$1.41 \times 10^2$	$0.63 \times 10^5$

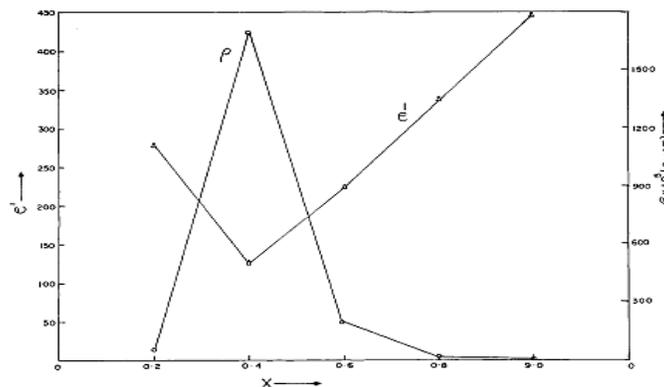

**Figure 3.** Plot of dielectric constant and resistivity ( $\rho$ ) vs erbium content for mixed Mn–Zn–Er ferrites.

**Structural and Dielectric Behaviour of Mn-Zn Er ferrites**

Rajesh Jain

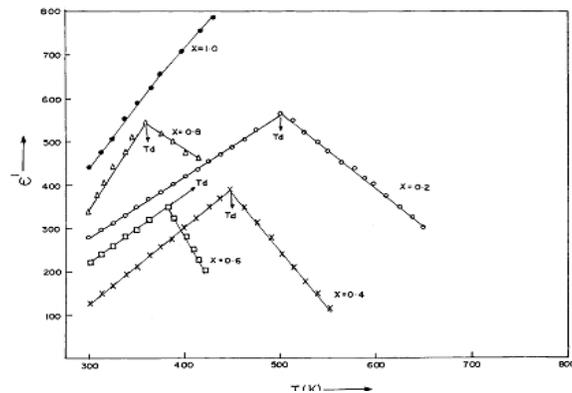

**Figure 4.** Variation of dielectric constant with temperature at 1 MHz for mixed Mn–Zn–Er ferrites.

product  $\epsilon''/\rho$  remains nearly constant as shown in table 2. A similar relationship between  $\epsilon'$  and  $\rho^{-1}$  was found by Koops (1951) and Venugopal Reddy and Seshagiri Rao (1985) in the case of Ni–Zn and Mn–Mg ferrites. Hudson (1968) has shown that the dielectric losses in ferrites are generally reflected in the resistivity measurements, materials with low resistivity exhibiting high dielectric losses and *vice versa*. Table 2 shows that this result holds good in the case of mixed Mn–Zn–Er ferrites too. Figure 3 shows that the plot of dielectric constant ( $\epsilon'$ ) vs the erbium content ( $X$ ) is an inverse image of that of the resistivity vs erbium content. This is a confirmation of the correlation between dielectric constant and resistivity proposed earlier (Rabinkin and Novikova 1960).

### 3.5 Variation of dielectric constant ( $\epsilon'$ ) with temperature

Figure 4 shows the variation of dielectric constant at 1 MHz with temperature for mixed Mn–Zn–Er ferrites.

**Table 3.** Curie temperatures ( $T_c$ ) and dielectric transition temperatures ( $T_d$ ) for mixed Mn–Zn–Er ferrites.

Sample no.	$X$	$T_c$ (K)	$T_d$ (K)
1.	0.2	502	500
2.	0.4	442	445
3.	0.6	380	382
4.	0.8	369	370
5.	1.0	–	–

The dielectric constant increases gradually with increasing temperature up to a certain temperature, which is designated as the dielectric transition temperature,  $T_d$ . However, beyond this temperature the values of dielectric constant for all the samples were found to decrease continuously. A similar temperature variation of the dielectric constant has been reported earlier (Olofa 1994; Yadav and Chowdhary 1994; Bera and Chowdhary 1995). The value of  $T_d(K)$  for each composition is given in table 3. The Curie temperature values,  $T_c(K)$  determined by the gravity method are also included in the table for the purpose

## Structural and Dielectric Behaviour of Mn-Zn Er ferrites

Rajesh Jain

of comparison. It can be seen from table 3 that the values of  $T_d(K)$  and  $T_c(K)$  are in good agreement, thereby indicating that the change in the behaviour of the dielectric constant with temperature may be due to a magnetic transition, where the material becomes paramagnetic. Similar agreement of  $T_c(K)$  and  $T_d(K)$  was also observed by Ramana Reddy *et al* (1999) in Co-Zn ferrites. No such dielectric transition was observed for the sample  $Mn_{0.58}Zn_{0.37}Er_{1.0}Fe_{1.05}O_4$  which suggests that this ferrite is paramagnetic at room temperature.

**\*Department of Physics  
L.B.S Govt. College  
Kotputli (Raj.)**

### References

1. Abdun A M 1999 *J. Magn. Magn. Mater.* 192 121 Bera S and Chowdhary R N P 1995 *Mater. Lett.* 22 197
2. Chandra Prakash and Bajal J S 1985 *J. Less Common Metals* 107 51
3. Elata A M A, Ahmed M A, Elhiti M A and Nimr M K El 1999
4. *J. Mater. Sci. Lett.* 18 563
5. Hudson A S 1968 *Marconi Rev.* 37 43
6. Iwauchi K 1971 *Jap. J. Appl. Phys.* 10 1520
7. Kolekar C B, Kamble P N, Kulkarni S G and Vaingankar A S 1995 *J. Mater. Sci.* 30 5784
8. Koops C G 1951 *Phys. Rev.* 83 121
9. Olofa S A 1994 *J. Magn. Magn. Mater.* 131 103
10. Rabinkin L I and Novikova Z I 1960 *Ferrites Minsk* (in Russian) p. 146
11. Ramana Reddy A V, Ranga Mohan G, Ravinder D and Boyanov B S 1999 *J. Mater. Sci.* 34 3169
12. Ranga Mohan G, Ravinder D, Ramana Reddy A V and Boyanov B S 1999 *Mater. Letts* 40 39
13. Rao B P and Rao K H 1997 *J. Mater. Sci.* B32 6049
14. Ravinder D 1988 *Electrical properties of lithium-zinc and lithium-cadmium ferrites*, Ph.D. Thesis, Osmania University, Hyderabad
15. Ravinder D 1993 *Phys. Status Solidi (a)* 139 K69 Ravinder D and Latha K 1999 *Mater. Letts* 41 247
16. Rezlescu N and Rezlescu E 1974 *Phys. Status Solidi* A23 575 Shaikh A M, Bellad S S and Chougule B K 1999 *J. Magn.*
17. *Magn. Mater.* 195 384
18. Venugopal Reddy P and Seshagiri Rao T 1985 *J. Less Common Metals* 105 63
19. Yadav K L and Chowdhary R N P 1994 *Mater. Lett.* 19 61